

## INVESTIGATION OF CUTTING TOOL INFLUENCE ON MACHINE TOOL POWER CONSUMPTION

Sabahudin Ekinović<sup>1</sup>, Edin Begović<sup>1</sup>, Irene Buj Corral<sup>2</sup>, Džavid Aličić<sup>3</sup>

<sup>1</sup>University of Zenica, Fakultetska 1, 72000 Zenica, B&H

<sup>2</sup>Politechnical University of Catalonia, UPC Barcelona, Spain

<sup>3</sup>Municipality Doboj-Jug, B&H

### ABSTRACT

*This paper deals with analysis of machine power consumption in case of machining 30CrNiMo8 steel by means of two different type of cutting tools, ceramic and cermets inserts. Factorial plan experiment has been performed in order to identify change of cutting forces in relation with the changes of cutting conditions. Experiment has been conducted in Laboratory for metal cutting – LORAM on University of Zenica. Kistler dynamometer Type 9265B is used to measure cutting force components  $F_x$ ,  $F_y$  and  $F_z$ . Regression analysis has performed on obtained data from which appropriate mathematical models are gained.*

**Keywords:** Cutting force, Power consumption, Regression

### 1. INTRODUCTION

Reducing energy consumption became one of the main goals in many researchs perform nowadays in machining materials area [1,2,3]. Beside economical effects that this reduction has, very important aspect is also its ecological impact. That is the reason for developing new systems like KERS – kinetic energy recovery system [1] or introducing new automated energy monitoring systems [2] in machining. Energy or power consumption in machining operation is a product of the main cutting force and cutting speed. It is used as one of the criterions for the selection of appropriate machine tools for cutting process performance. Determination of adequate cutting conditions, in for example turning process, is more or less starting with selection of appropriate cutting inserts to be used in that process. The producers of cutting tools gives recommended speed and feed for their cutting tools, but none of them will give information about power consumption for that tool. In literature one can found data like is specific power consumption for blunt or sharp tool. Those data are used in calculation of power consumption in relation with cutting conditions. The aim of this investigation is to give an example of establishing relationships between cutting conditions and power consumption in case of machining same material with two different type of cutting inserts, cermet and ceramic. The cutting geometries of the selected inserts are different. Hence, the change in power consumption will dependent only on the cutting inserts geometry.

### 2. EXPERIMENTAL SET-UP

The experiment is conducted in Laboratory for metal cutting and machine tools – LORAM on University of Zenica. Factorial plan 2<sup>3</sup> is used for designing experimental investigation. Table 1 shows controlled factors with their levels.

Table 1. Level of factors

Level	Factor		
	Cutting speed, $v$ [m/min]	Feed, $s$ [mm/o]	Depth of cut, $a$ [mm]
(+1)	200	0,2	0.75
(-1)	100	0,05	0.25

Table 2. Plan matrix of experiment

Run	Plan matrix				Cutting inserts			
	$X_0$	$X_1$ (v)	$X_2$ (s)	$X_3$ (a)	CNMG (cermet)		CNGA (ceramic)	
					F	ln F	F	ln F
1.	+1	-1	-1	-1	184,145	5,216	181,734	5,2025
2.	+1	+1	-1	-1	58,223	4,064	163,817	5,099
3.	+1	-1	+1	-1	261,686	5,567	354,923	5,872
4.	+1	+1	+1	-1	213,877	5,365	213,877	5,365
5.	+1	-1	-1	+1	293,237	5,681	332,265	5,806
6.	+1	+1	-1	+1	281,084	5,639	292,83	5,68
7.	+1	-1	+1	+1	576,046	6,356	576,046	6,356
8.	+1	+1	+1	+1	644,276	6,468	644,276	6,468

### 3. RESULTS AND DISCUSSION

After processing these data following results are obtained:

#### SUMMARY OUTPUT for CERMET

Regression Statistics					
Multiple R	0,934885296				
R Square	0,874010517				
Adjusted R Square	0,779518405				
Standard Error	0,349200515				
Observations	8				
ANOVA					
	df	SS	MS	F	Significance F
Regression	3	3,383702	1,127901	9,249561	0,028481
Residual	4	0,487764	0,121941		
Total	7	3,871466			
	Coefficients	Standard Error	t Stat	P-value	
Intercept	9,897086366	1,824951	5,423206	0,005605	
ln v	-0,46310511	0,356233	-1,30001	0,26345	
ln s	0,569143194	0,178117	3,19534	0,033047	
ln a	0,89476516	0,224758	3,981013	0,016387	

#### SUMMARY OUTPUT for CERAMIC

Regression Statistics					
Multiple R	0,965717				
R Square	0,932609				
Adjusted R Square	0,882066				
Standard Error	0,17291				
Observations	8				
ANOVA					
	df	SS	MS	F	Significance F
Regression	3	1,655002	0,551667	18,45174	0,008322
Residual	4	0,119591	0,029898		
Total	7	1,774593			
	Coefficients	Standard Error	t Stat	P-value	
Intercept	8,318321	0,903642	9,205329	0,000774	
ln v	-0,22524	0,176392	-1,27693	0,270716	
ln s	0,409996	0,088196	4,648684	0,009671	
ln a	0,630682	0,111291	5,666957	0,004782	

Since the P-value in ANOVA tables for both cases is bigger than 0.05, with 95% confidence level the cutting speed can be considered as an insignificant factor in both of regression models. For purpose of further calculations its value will be set to level 0 ( $v=150$  m/min).

After decoding linear regression models, following polynomial functions are gained:

CNMG cermets: 
$$F_{\text{cermet}} = 19870.67 \frac{s^{0.5694} \cdot a^{0.8945}}{v^{0.4631}} \quad \dots(1)$$

CNGA ceramic: 
$$F_{\text{ceramic}} = 4098.187 \frac{s^{0.4099} \cdot a^{0.6307}}{v^{0.2252}} \quad \dots(2)$$

For  $v=150$  m/min the models became:

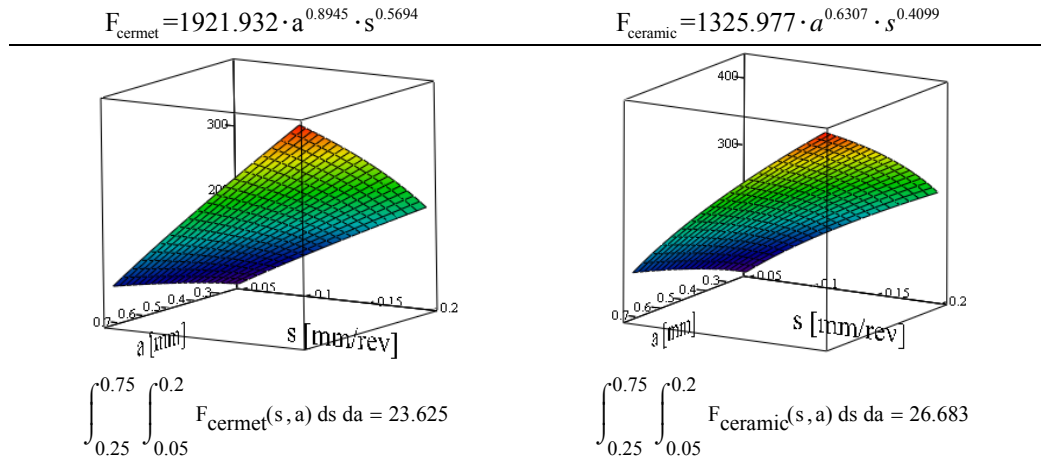


Figure 1. 3D plot of cutting forces for cermet and ceramic inserts

Obviously, ceramic cutting inserts, in comparing with cermets inserts, require more energy to be spent in machining process.

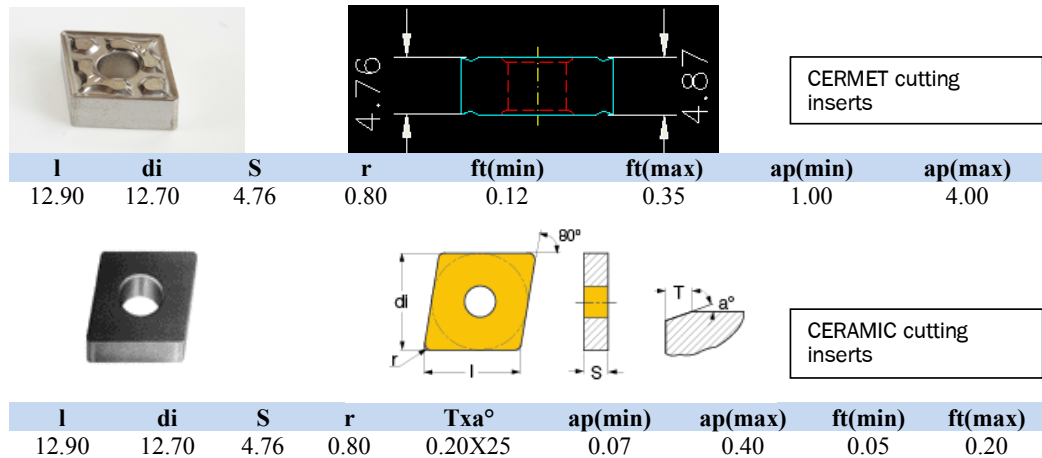


Figure 2. Cutting inserts data [5]

Cutting power consumption calculation is based on cutting force components measurement, figure 1. Roughly, one can state that cutting power is product of cutting force and cutting speed. In this case, that power consumption can be expressed by Equations (3) and (4). Equation (5) is used to calculate difference between the two cases. Its graphical interpretation is shown in figure 3.

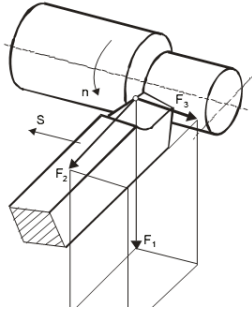


Figure 2. Cutting force components direction

$$P_{cermet}(s,a) = \frac{F_{cermet}(s,a) \cdot v}{6 \cdot 10^4} [W] \quad \dots(3)$$

$$P_{ceramic}(s,a) = \frac{F_{ceramic}(s,a) \cdot v}{6 \cdot 10^4} [W] \quad \dots(4)$$

$$\Delta P(s,a) = P_{ceramic}(s,a) - P_{cermet}(s,a), [W] \quad \dots(5)$$

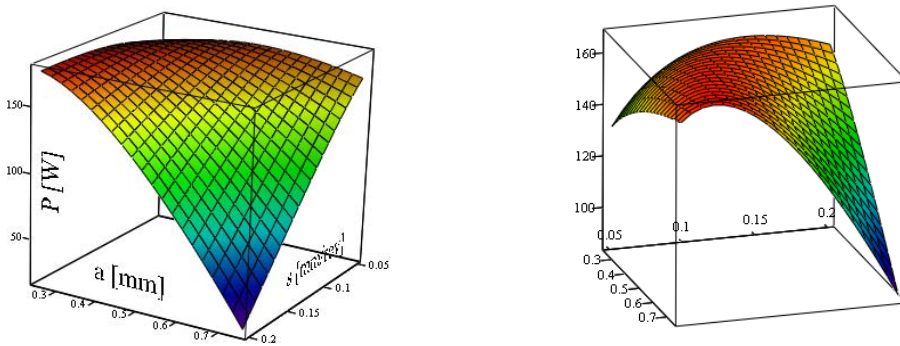


Figure 3. Difference in power consumption for different cutting tools

#### 4. CONCLUSION

The results show that power consumption depends not only on cutting conditions but also on cutting insert geometry. In the presented investigation, machining with ceramic inserts consumes more energy than machining with cermet inserts. The main reason is notable in figure 2 – cutting insert data, and it is the fact that ceramic inserts are supposed to cut with depths more than 1 mm, which is actually bigger than the upper depth of cut's level used in experiment. That means, bigger the depth of cut (as well as feed) smaller the difference between energy consumption. On the other hand, at the same time, bigger feed and bigger depth of cut means higher cutting force and consequently higher the absolute value of energy consumption. By coupling the presented methodology and additional machinability parameters like surface roughness, for example, it should be possible to optimize energy consumption in machining processes and make an environmentally friendly choice of cutting insert geometry.

#### 6. REFERENCES

- [1] Aman Aggarwal, Hari Singh, Pradeep Kumar, Manmohan Singh: Optimizing power consumption for CNC turned parts using response surface methodology and Taguchi's technique - A comparative analysis, Journal of Materials Processing Technology, Volume 200, Issues 1-3, 8 May 2008, Pages 373-384.
- [2] Nancy Diaz, Moneer Helu, Andrew Jarvis, Stefan Tönissen, David Dornfeld, Ralf Schlosser: Strategies for Minimum Energy Operation for Precision Machining, The Proceedings of MTTRF Annual Meeting, 2009
- [3] A. Vijayaraghavan, D. Dornfeld: Automated energy monitoring of machine tools, CIRP Annals - Manufacturing Technology 59 (2010) 21–24
- [4] S. Ekinović, Obradljivost čeličnih materijala / Machinability of steels, Faculty of Mechanical Engineering in Zenica, 1999.
- [5] www.iscar.com, ISCAR web site